

K. LABER\*, H. DYJA\*, M. KWAPISZ\*

## NUMERICAL MODELLING OF THE COOLING ABILITY OF DEVICE FOR THE PLAIN ROUND BARS ACCELERATED COOLING PROCESS

## NUMERYCZNE MODELOWANIE ZDOLNOŚCI CHŁODZĄCEJ URZĄDZENIA DO PRZYSPIESZONEGO CHŁODZENIA PRĘTÓW OKRĄGLYCH GŁADKICH

The paper presents numerical modelling results of the band accelerated cooling during rolling process. For the numerical modelling the Forge3® and the SortRoll computer programs were used, which based on finite element method.

Research were carried out for one of the bar rolling mill technological conditions. The studies were carried out for 30mm-diameter plain round bars. Constructional steel S355J2G3 (according to DIN St 52-3) was used for the research.

The paper purpose was determination of the cooling ability of device for accelerated cooling process to checking possibility of the using this device in the rolling line, during normalizing rolling process. Investigation results elaborated in the paper made the basis for determination of the heat convection coefficients between cooled band and water for different pressure and water flow.

*Keywords:* numerical modelling, accelerated cooling, bars normalizing rolling process, S355J2G3 constructional steel

W pracy przedstawiono wyniki numerycznego modelowania procesu przyspieszonego chłodzenia pasma podczas walcowania. Do modelowania matematycznego wykorzystano komputerowe programy FORGE3® oraz SortRoll oparte na metodzie elementów skończonych.

Badania przeprowadzono dla warunków technologicznych jednej z walcowni prętów. Przedstawione w pracy badania przeprowadzono dla prętów okrągłych gładkich o średnicy 30mm. Materiałem wykorzystanym do badań była stal konstrukcyjna S355J2G3.

Celem pracy było określenie warunków chłodzenia w urządzeniu do przyspieszonego chłodzenia pasma pod kątem sprawdzenia możliwości zastosowania tego urządzenia do chłodzenia prętów w ciągu walcowniczym, podczas walcowania normalizującego. Opracowane wyniki badań stanowiły podstawę do wyznaczenia współczynników przejmowania ciepła przy chłodzeniu pasma wodą dla zmiennego ciśnienia i różnych przepływów wody.

### 1. Introduction

There are composite heat exchange conditions inside devices for the band accelerated cooling process during or after the rolling process. It is convection to the transfluent water, radiation to the surrounding steam atmosphere and convection to the water and steam mixture. There are a little published methods of the total heat exchange coefficient calculation in this conditions [1]. Differences of the heat exchange coefficient values inside cooling devices come from using by individual authors different research methods for calculation of this coefficient, among other things [2]. Moreover there are a little data and formulas in the technical literature for accurately calculation of heat exchange coefficients dur-

ing band cooling process by using high-pressure water systems [3].

### 2. Purpose and scope of the study

The paper purpose was determination of the cooling ability of device for accelerated cooling process to checking possibility of using this device in the rolling line, during normalizing rolling process. Investigation results elaborated in the paper made the basis for determination of the heat exchange coefficients between cooled band and water for different pressure and water flow value.

Research were carried out for one of the bar rolling mill technological conditions. The studies were carried

\* CZĘSTOCHOWA UNIVERSITY OF TECHNOLOGY, FACULTY OF MATERIAL PROCESSING TECHNOLOGY AND APPLIED PHYSICS, INSTITUTE OF MODELLING AND AUTOMATION OF PLASTIC WORKING PROCESSES, 42-200 CZĘSTOCHOWA, 19 ARMII KRAJOWEJ AV., POLAND

out for 30mm-diameter plain round bars. Constructional steel S355J2G3 (according to DIN St 52-3) [4] was used for the research.

As a results of carried out computer simulations the temperature distribution in the material for analyzed variants were obtain.

In the next stage of this paper numerical modeling of the normalizing rolling process with accelerated cooling of band in the final stage of the rolling process were carried out. In this investigation heat exchange coefficients between band and cooling medium (water), which were determinated with allowance of cooling possibilities of investigated device for band accelerated cooling were used.

### 3. Analysis of the investigation results

Currently, the process of rolling 30 mm-diameter round bars is carried out in 14 successive passes. After

the band had been rolled in 14 rolling stands, it was air cooled up to the point of entering the accelerated cooling device.

The rolling process parameters used in numerical modelling of rolling 30 mm-diameter plain round bars are given in Table 1. The data in this table were calculated based on relationships described in reference [5]. The temperature of the rolls was assumed based on industrial test results [6].

Table 2 shows data concerning water flow and pressure for respective cooling variants, as obtained from the Rolling Mill Department. This table provides also the values of the heat convection coefficient between the material being cooled and the water, as selected based on the obtained industrial test results using the inverse method, which are described in detail in work [7].

Figures 1÷2 represent band temperature distributions, as computed numerically using the FORGE3® software [8] immediately before and after the cooling device, respectively, for the variants under analysis.

TABLE 1

Input data for the computer simulations of the 30 mm-diameter plain round bars rolling process

| Air temperature, [°C] | Rolls temperature, [°C] | Friction factor, [-] | Friction coefficient, [-] | Coefficient of heat transfer between band and air, [W/m <sup>2</sup> K] | Coefficient of heat transfer between band and rolls, [W/m <sup>2</sup> K] |
|-----------------------|-------------------------|----------------------|---------------------------|---|---|
| 20                    | 60                      | 0,8                  | 0,3                       | 100   | 3000  |

TABLE 2

Main parameters of the cooling process used during research

|           | Band linear speed [m/s] | Accelerated cooling time of band [s] | Water flow [m <sup>3</sup> /h] | Water pressure [bar] | Heat convection coefficient between material and cooling medium (water) [W/m <sup>2</sup> K] |
|-----------|-------------------------|--------------------------------------|--------------------------------|----------------------|--|
| Variant 1 | 3,19                    | 0,43                                 | 110                            | 12                   | 18000  |
| Variant 2 | 3,19                    | 0,43                                 | 75                             | 6                    | 9000   |
| Variant 3 | 6,50                    | 0,21                                 | 75                             | 6                    | 18000  |
| Variant 4 | 6.50                    | 0,21                                 | 110                            | 12                   | 9000   |

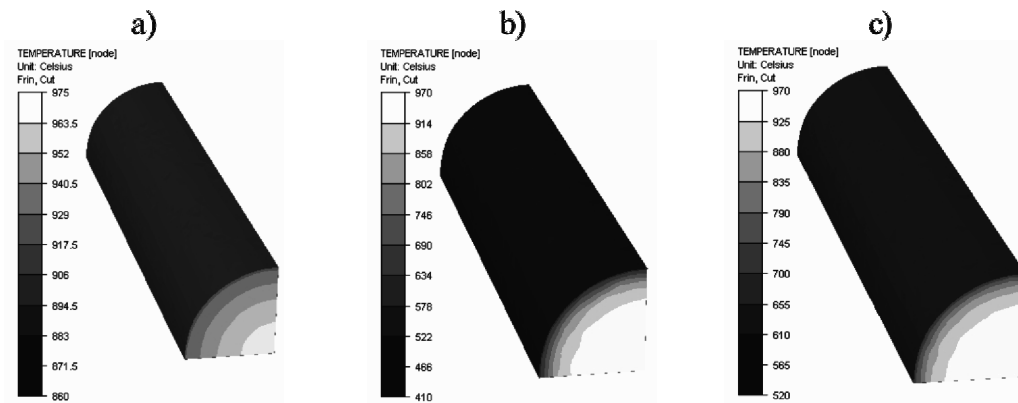


Fig. 1. Band temperature distribution [ $^{\circ}\text{C}$ ] computed for the variants 1 and 2: a) before cooling device (variant 1 and 2), b) after cooling device (variant 1), c) after cooling device (variant 2)

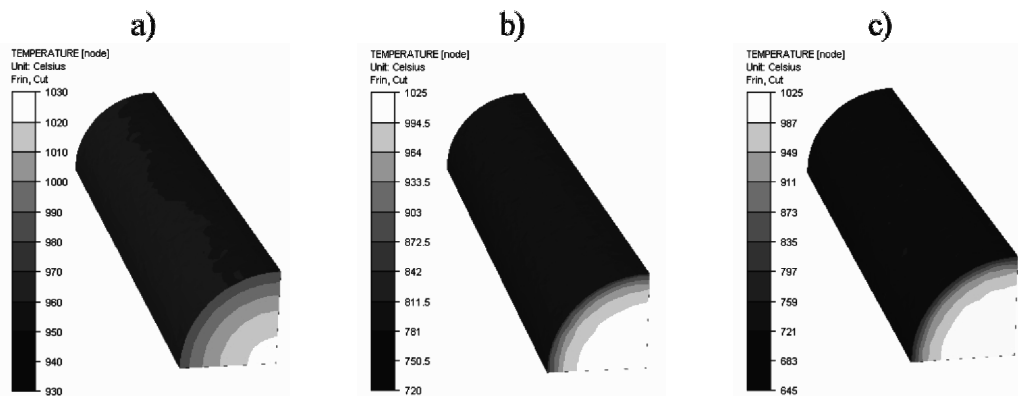


Fig. 2. Band temperature distribution [ $^{\circ}\text{C}$ ] computed for the variants 3 and 4: a) before cooling device (variant 3 and 4), b) after cooling device (variant 3), c) after cooling device (variant 4)

By analyzing the data in Figure 1a it was found that the average band temperature immediately before the cooling device for Variant 1, as computed numerically, was  $950^{\circ}\text{C}$ , while the band surface temperature was approx.  $927^{\circ}\text{C}$ . The band temperature difference on the cross-section was in this case about  $23^{\circ}\text{C}$ .

After analysis of the data in Figure 1b it was found that the average band temperature immediately after the cooling device for Variant 1, as computed numerically, was in this case about  $795^{\circ}\text{C}$ , while the band surface temperature was approx.  $615^{\circ}\text{C}$ . The band temperature difference on the cross-section was about  $355^{\circ}\text{C}$ .

Upon the analysis of the test results for Variant 2 (Fig. 1c) it was found that the average temperature of the band immediately after the cooling device, as computed numerically, was approx.  $850^{\circ}\text{C}$ , while the band surface temperature was about  $720^{\circ}\text{C}$ . Whereas, the band temperature difference on the cross-section was about  $250^{\circ}\text{C}$ .

By comparing the temperature test results for Variants 1 and 2 it is found that better results were obtained using Variant 2. The temperature difference on the band cross-section, as obtained using Variant 2, is smaller compared to Variant 1, which will result in faster equalization of the band cross-section temperature at the subsequent stages of the rolling process. However, reducing the rolling speed from  $6.5\text{ m/s}$ , as presently used, down to a speed of  $3.19\text{ m/s}$  would lower the output of the Rolling Mill.

By analyzing the test results for Variant 3 (Fig. 2a) it was found that the average temperature of the band immediately before the cooling device, as computed numerically, was approx.  $1002^{\circ}\text{C}$ , while the band surface temperature was about  $980^{\circ}\text{C}$ . The band temperature difference on the cross-section was in this case about  $22^{\circ}\text{C}$ .

From the analysis of the data in Figure 2b it was found that the average temperature of the band immediately after the cooling device for Variant 3, as computed

numerically, was in this case about 940°C, while the band surface temperature was approx. 855°C. The band temperature difference on the cross-section was in this case about 170°C.

Upon the analysis of the test results for Variant 4 (Fig. 2c) it was found that the average temperature of the band immediately after the cooling device, as computed numerically, was approx. 904°C, while the band surface temperature was about 785°C. Whereas, the band temperature difference on the cross-section was about 238°C.

By comparing, in turn, the temperature test results obtained for Variants 3 and 4 it is found that better results were obtained using Variant 3. The temperature difference on the band cross-section, as obtained using Variant 3, is smaller compared to Variant 4, which will result in faster equalization of the band cross-section temperature at the subsequent stages of the rolling process.

When analyzing the test results represented in Figures 1b, 1c and 2b, 2c it can be observed that primarily the thin surface layers of the band undergo rapid cooling as a result of accelerated cooling applied.

By comparing the temperature distribution results obtained from numerical modelling with the temperature values measured under industrial conditions using a thermovision camera, which are described in detail in work [7], it is found that the band temperature values obtained from numerical modelling correspond with high accuracy to the values measured in industrial conditions. The error between the band surface temperature values computed numerically and measured in industrial conditions ranged from 1.5% to 3.7%.

The temperature distribution results for all analyzed

variants before and after the cooling device are summarized in Table 3.

This table provides also the temperature values measured in industrial conditions along with the error between the temperature values computed numerically and measured.

By comparing all the test results it is found that the best cooling variant is Variant 3. The temperature difference on the band cross-section, as obtained using Variant 3, is the lowest of all the variants examined, and what is more, this variant does not require the rolling speed to be reduced, owing to which the Rolling Mill's output will not decrease.

Within the next part of the work numerical modelling of the process of normalizing rolling of 26 mm-diameter round bars was carried out, while using accelerated cooling according to Variant 3.

To assure the average band temperature after the normalizing rolling process for the steel under examination to be obtained at a level of 900°C [9], two sections of accelerated cooling were employed. Modifications to the technology of rolling 26 mm-diameter round plain bars in 14 successive passes were proposed, which consisted in the transferring of rolling from rolling stands no. 13 and 14 to rolling stands no. 17 and 18. The implemented modifications included also the use of accelerated cooling after rolling stand no. 12. For numerical studies, the SortRoll program [10] was employed.

The values of heat transfer coefficients and other data required for performing computer simulation of the rolling process under analysis, either calculated or taken from literature [2, 11÷14], are given in Table 4.

TABLE 3

Temperature distribution results during accelerated cooling process of the 30 mm-diameter plain round bars

| Variant number |        | Computed band temperature, [°C] |                             |   |                                     |   | Lateral surface temperature measured in the industrial conditions, [°C] | Error $\delta$ , [%] |
|----------------|--------|---------------------------------|-----------------------------|---|-------------------------------------|---|---|----------------------|
|                |        | Average temperature             | Lateral surface temperature | Temperature difference on the cross-section | Decrease of the average temperature | Decrease of the lateral surface temperature |   |                      |
| V1             | Before | 950                             | 927                         | 23  | 155                                 | 312   | –   | –                    |
|                | After  | 795                             | 615                         | 355   |                                     |   | 602   | 2,2                  |
| V2             | Before | 950                             | 927                         | 23  | 100                                 | 207   | –   | –                    |
|                | After  | 850                             | 720                         | 250   |                                     |   | 701   | 2,7                  |
| V3             | Before | 1002                            | 980                         | 22  | 62                                  | 125   | –   | –                    |
|                | After  | 940                             | 855                         | 170   |                                     |   | 844   | 1,3                  |
| V4             | Before | 1002                            | 980                         | 22  | 98                                  | 195   | –   | –                    |
|                | After  | 904                             | 785                         | 238   |                                     |   | 757   | 3,7                  |

TABLE 4

Input data for the computer simulations of the 26 mm-diameter plain round bars rolling process

| Ambient temperature [°C] | Rolls temperature [°C] | Water temperature [°C] | Friction factor [-] | Heat transfer coefficient between band and air [W/m <sup>2</sup> ·K] | Heat transfer coefficient between band and rolls [W/m <sup>2</sup> ·K] | Heat convection coefficient between band and water [W/m <sup>2</sup> ·K] |
|--------------------------|------------------------|------------------------|---------------------|--|--|--|
| 20                       | 60                     | 25                     | 0,8                 | 107 ÷ 138  | 3000 ÷ 9815  | 9000<br>(in the first section of the cooling device)                     |
|                          |                        |                        |                     |  |  | 9000<br>(in the second section of the cooling device)                    |

The main rolling process parameters, as obtained from the Rolling Mill Department, are given in Table 5. This table provides also average strip temperatures before and after each pass, as obtained from numerical modelling, which included accelerated cooling after rolling stand no. 12. The initial temperature value was assumed based on measurements taken during the actual rolling process using a thermovision camera.

The temperature distribution and the average band temperatures obtained from the performed computer simulations which allowed for accelerated cooling after rolling stand no. 12 are shown in Figs. 3÷8. These figures represent results for band temperature distribution on the cross-section and over the length of the band.

TABLE 5

Main parameters of the 26 mm-diameter plain round bars normalizing rolling process

| Stand no. | Groove type         | Band output speed, [m/s] | Band average temperature, [°C] |            |
|-----------|---------------------|--------------------------|--------------------------------|------------|
|           |                     |                          | before pass                    | after pass |
| 1H        | Box                 | 0,21                     | 1120                           | 1110       |
| 2V        | Box                 | 0,27                     | 1103                           | 1094       |
| 3 H       | Box-oval            | 0,37                     | 1088                           | 1081       |
| 4V        | Round               | 0,49                     | 1075                           | 1070       |
| 5 H       | Oval                | 0,72                     | 1064                           | 1059       |
| 6V        | Round               | 0,98                     | 1054                           | 1052       |
| 7 H       | Oval                | 1,35                     | 1041                           | 1040       |
| 8V        | Round               | 1,86                     | 1037                           | 1038       |
| 9 H       | Oval                | 2,48                     | 1037                           | 1038       |
| 10V       | Round               | 3,33                     | 1036                           | 1040       |
| 11 H      | Oval                | 4,39                     | 1037                           | 1038       |
| 12V       | Round               | 4,96                     | 1035                           | 1037       |
| 13 H      | Accelerated cooling |                          |                                |            |
| 14V       |                     |                          |                                |            |
| 15 H      | –                   |                          |                                |            |
| 16V       | –                   |                          |                                |            |
| 17 H      | Oval                | 6,34                     | 898                            | 898        |
| 18V       | Round               | 7,56                     | 896                            | 896        |

H – horizontal rolling stand, V – vertical rolling stand

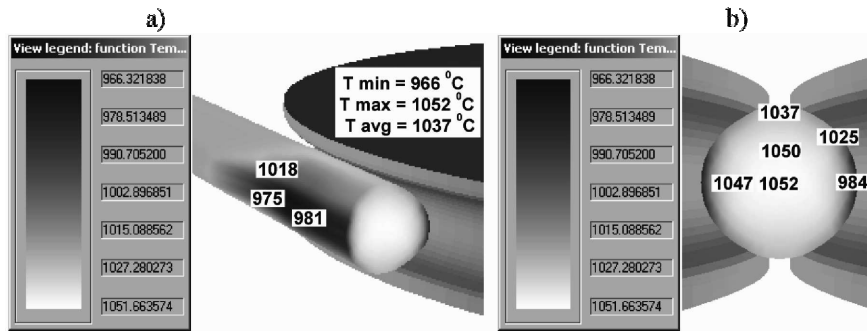


Fig. 3. Band temperature distribution [°C] after rolling stand no. 12: a) – over the length of the band, b) – on the band cross-section

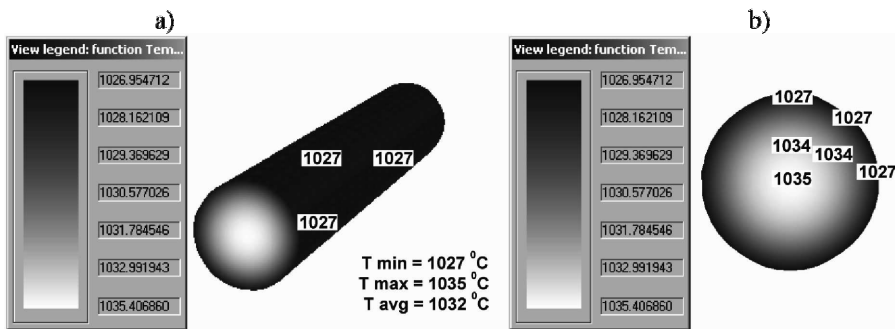


Fig. 4. Band temperature distribution [°C] before the first section of the cooling device installed in the rolling stand no. 13 place: a) – over the length of the band, b) – on the band cross-section

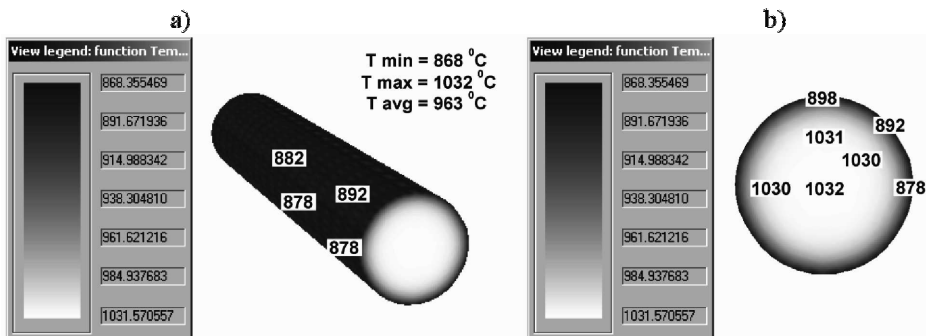


Fig. 5. Band temperature distribution [°C] after the first section of the cooling device installed in the rolling stand no. 13 place: a) – over the length of the band, b) – on the band cross-section

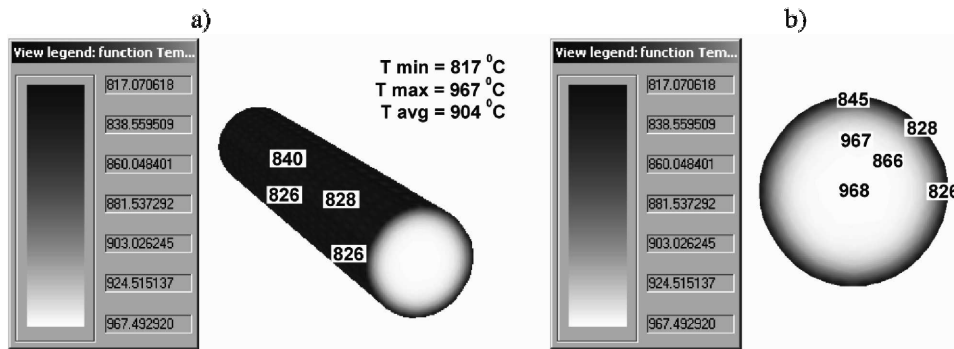


Fig. 6. Band temperature distribution [°C] after the second section of the cooling device installed in the rolling stand no. 14 place: a) – over the length of the band, b) – on the band cross-section

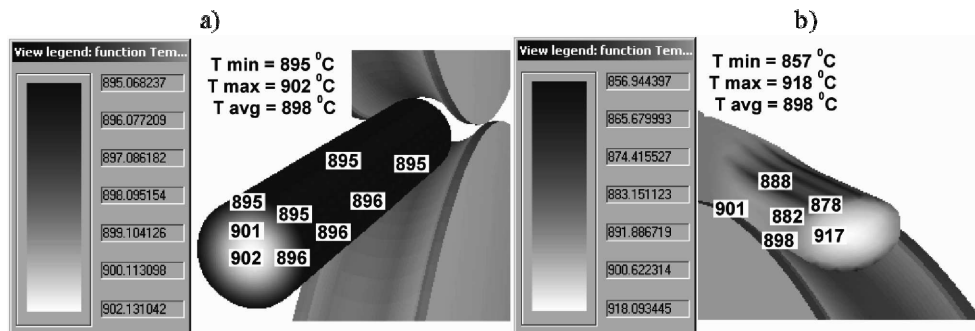


Fig. 7. Band temperature distribution [°C] in the rolling stand no. 17: a) – before pass, b) – after pass

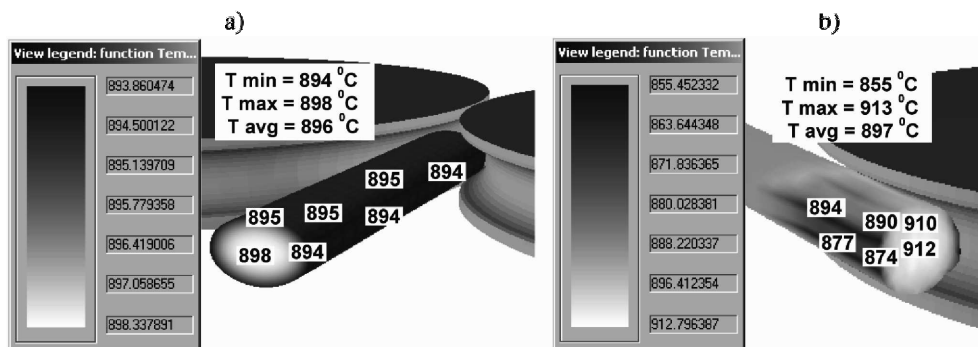


Fig. 8. Band temperature distribution [°C] in the rolling stand no. 18: a) – before pass, b) – after pass

From the obtained results it has been found that the average temperature of the strip after rolling according to the new rolling scheme was approx. 900°C. So, it can be stated that the proposed method of cooling enables the required strip temperature level after rolling to be obtained.

#### 4. Conclusions

From the conducted studies on the cooling capability of the plain round bar accelerated cooling device and upon the analysis of the obtained results, the following conclusions have been drawn:

- the band temperature distribution results obtained from numerical modelling for respective cooling variants correspond with high accuracy to the temperature values measured in industrial conditions;
- the initial and boundary conditions taken for numerical modelling were determined correctly;
- from the obtained test results it has been established that the best conditions for the accelerated cooling of band are provided by using Variant 3 of cooling;
- in the Bar Rolling Mill under study, it is possible to reduce the average band temperature down to a value of approx. 900°C, which is required for normalizing rolling;



- obtaining an average band temperature of about 900°C requires two accelerated cooling sections to be employed before the last two rolling stands;
- increasing the distance between the end passes will reduce the temperature difference on the rolled band cross-section, which forms as a result of applying accelerated cooling;
- installing a cooling device with the parameters and sizes examined is technically possible in the conditions of the Rolling Mill under study;
- the reduction of the rolling end temperature will have a favourable effect on the properties and structure of the finished product.

## REFERENCES

- [1] S. Kajzer, R. Kozik, R. Wusatowski, Wybrane zagadnienia z procesów obróbki plastycznej metali. Projektowanie technologii (Selected problems of metals plastic working processes. The design of technologies). The Publishing House of the Silesian University of Technology, ISBN 83-85718-72-9, pp. 63, 69-85, 100-102, Gliwice (1997).
- [2] A. A. Minaev, S. V. Ustimenko, Kontroliruemaya prokatka sortovoy stali, Izdatelstvo Metallurgya, ISBN 5-229-00296-4, pp. 6, 10-11, 13, 20-68, Moskva (1990).
- [3] C. Devadas, I.V. Samarasckera, Heat transfer during hot rolling of steel strip, *Ironmaking and Steelmaking* **13**, 6, 311-321 (1986).
- [4] Polish Standard PN-EN 10025: Hot rolled products of unalloyed constructional steels. The technical specifications of delivery. The Polish Standardization Committee, ISBN 83-243-0390-1, pp. 6, 18-23, 33 (2002).
- [5] K. Laber, Modelowanie i optymalizacja procesów regulowanego walcowania i kontrolowanego chłodzenia wyrobów walcowni bruzdowych (Modelling and optimization of the processes of controlled rolling and controlled cooling of shape mill products). The doctoral thesis, pp. 40-43, 88, Czestochowa (2008).
- [6] K. Laber, H. Dyja, Przemysłowe badania temperatury walców podczas walcowania prętów okrągłych w walcowni ciągłej (Industrial testing of rolls temperature during rolling of round bars in the Continuous Rolling Mill). Proceedings of the 10<sup>th</sup> International Scientific Conference on „New technologies and achievements in metallurgy and materials engineering”. The joint publication technically edited by Prof. Henryk Dyja, Czestochowa University of Technology, Faculty of Process & Materials Engineering and Applied Physics, Series: Conference Transactions No. 1, Czestochowa, 5 June, 2009, The Publishing House of the Faculty of Process & Materials Engineering and Applied Physics, ISBN 978-83-87745-18-9, ISSN 2080-2080, pp. 56-59, Czestochowa (2009).
- [7] K. Laber, H. Dyja, Zastosowanie techniki termowizyjnej do badania zdolności chłodzącej urządzenia do przyspieszonego chłodzenia prętów okrągłych gładkich (The application of the thermovision technique for the study of the cooling capability of the plain round bar accelerated cooling device). Proceedings of the 18<sup>th</sup> International Scientific & Technical Conference on „Production and Management in Metallurgy”, 01-03.07.2010. Zakopane, The „Hutnik -Wiadomości Hutnicze” Journal, No. 9/2010, HUTNAD 77 (5) 441-564 (2010), ISSN 1230-3534, The Sigma-Not Sp. z o. o. Publishing House, pp. 537-539, Warsaw (2010).
- [8] FORGE3® Reference Guide Release 6.2. Sophia-Antipolis, November (2002).
- [9] L. A. Dobrzański, Metaloznawstwo z podstawami nauki o materiałach (Physical metallurgy with the fundamentals of materials science), Edition 3, The Scientific and Technical Publishers, ISBN 83-202086-5, pp. 219, 269, Warsaw (1996).
- [10] V. Danchenko, H. Dyja, L. Lesik, L. Mashkin, A. Milenin, Technologia i modelowanie procesów walcowania w wykrojach (The technology and modelling of grooved rolling processes), Czestochowa University of Technology, Teaching Publications of the Faculty of Process & Materials Engineering and Applied Physics, Series: Metallurgy No. 28, The Publishing House of the Faculty of Process & Materials Engineering and Applied Physics, ISBN 83-87745-66-9, pp. 530-579, Czestochowa (2002).
- [11] S. Kajzer, R. Kozik, R. Wusatowski, Walcowanie wyrobów długich. Technologie walcownicze (Rolling of long products. Rolling technologies), The Publishing House of the Silesian University of Technology, ISBN 83-7335-236-8., pp. 77, 84, 85, Gliwice (2004).
- [12] M. Pietrzyk, Metody numeryczne w przeróbce plastycznej metali (Numerical methods in the plastic working of metals), Skrypty Uczelniane No. 1303, Edition 1, The AGH Publishers, PL ISSN 0239-6114, pp. 156-157, Krakow (1992).
- [13] E. I. Kazancev, A. M. Kushnir, Metodicheske ukazaniya k rastchetu temperaturnogo sostoyaniya metalla pri prokatke po kursu „Metallurgicheskaya teplotekhnika”, Ministerstvo Vysshego i Srednego Spetsyalnogo Obrazovaniya USSR, Donecky Ordena Trudovogo Krasnogo Znameny Politekhnikhesky Institut, Doneck DPI, 6-8 (1987).
- [14] S. Mróz, Modelowanie walcowania prętów żebrowanych otrzymanych metodą wzdłużnego rozdzielenia pasma (Modelling of the rolling of ribbed bars obtained by the longitudinal strip separation method). Proceedings of the Conference on „Physical and Mathematical Modelling of Plastic Working Processes”, Warsaw 20-21.05.2005, Scientific Works – Mechanics, Vol. 207, The Publishing House of the Warsaw University of Technology, ISSN 0137-2335, p. 66, Warsaw (2005).